

AD-A121 614

EFFECT OF SIZE OF NONREINFORCING FILLERS ON MECHANICAL  
PROPERTIES OF ELASTOMERS(U) AKRON UNIV OH INST OF  
POLYMER SCIENCE P DREYFUSS ET AL. OCT 82 TR-21

1/1


UNCLASSIFIED

N00014-76-C-0408

F/G 11/9

NL


END  
DATE  
FILMED  
1-80  
DTIC

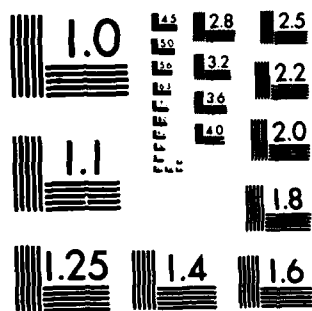

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963 A

AD A121614

DTIC FILE COPY

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 21	2. GOVT ACCESSION NO. AD-A121614	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Effect of Size of Nonreinforcing Fillers on Mechanical Properties of Elastomers		5. TYPE OF REPORT & PERIOD COVERED Technical Report
7. AUTHOR(s) P. Dreyfuss and Y. Eckstein		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Institute of Polymer Science The University of Akron Akron, Ohio 44325		8. CONTRACT OR GRANT NUMBER(s) N00014-76-C-0408
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Power Program, Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 092-555
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE October, 1982
		13. NUMBER OF PAGES 34
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) According to attached distribution list. Approved for public release; <del>distribution unlimited</del>		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) DTIC NOV 19 1982		
18. SUPPLEMENTARY NOTES Accepted for publication in I & EC Product Research and Development		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Nonreinforcing fillers, mechanical properties, elastomers, swelling ratio, filler size, stress strain properties		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) A literature survey of the effect of the particle size of nonreinforcing fillers on the mechanical properties of elastomers and a critical evaluation of the literature results compared to new data from the authors' laboratory were made. The effect of filler content was also considered. The study demonstrated that qualitatively mechanical properties of filled elastomers in general are a complex function of the filler's particle size (surface to volume ratio) and loading (distance between particles). Quantitatively, properties were dependent on the system being studied. Relative		

DD FORM 1473  
1 JAN 73EDITION OF 1 NOV 68 IS OBSOLETE  
S/N 0102-LF-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

82 11 19 011

modulus, relative breaking elongation, relative breaking stress and swelling ratios were functions of the reciprocal size of the filler up to a particle size of about 140  $\mu$ m. With particles of larger diameter the influence on these properties was smaller. When the distance between particles is smaller than their size, interactions in the volume surrounding the particles may become the dominant variable. ←

*the 20 m*

OFFICE OF NAVAL RESEARCH

Contract N00014-76-C-0408

Project NR 092-555

Technical Report No. 21

EFFECT OF SIZE OF NONREINFORCING FILLERS ON  
MECHANICAL PROPERTIES OF ELASTOMERS

by

P. Dreyfuss and Y. Eckstein

Institute of Polymer Science  
The University of Akron  
Akron, Ohio 44325

October, 1982

Reproduction in whole or in part is permitted for any purpose of  
the United States Government

Approved for Public Release; Distribution Unlimited



## INTRODUCTION

A composite propellant consists of a mixture of oxidizer and fuel. The most widely used formulations include ammonium perchlorate as the oxidizer and polybutadiene as the fuel. Investigations in our laboratory are directed toward developing and understanding the fundamental factors that control adhesion between oxidizer particles and the fuel. When the stress is applied, poor adhesion between these components may result in formation of voids at the filler-matrix interface, and thus affect the uniformity of performance.

The adhesion between flat surfaces, such as coated and uncoated plates or slides, and cured polybutadiene has been studied as a model system for a propellant, when the emphasis of the study was focussed on the interface alone. These studies on model systems (Ahagon and Gent, 1975; Runge and Dreyfuss, 1979; Dreyfuss et al. 1981) have proven to be very helpful in elucidating the effect of chemical bonding on adhesion.

In real systems, the oxidizer is present in the form of particles and to gain a complete understanding studies must be carried out with composites containing particles. The adhesion between powdered ammonium perchlorate and polybutadiene, and ways to improve it have been the subject of several publications, for example, Granstein and Williams (1974), Markin and Williams (1974), and Schwarz and Lowrey (1967). Their studies have shown that unmodified crystalline material in these composites functions as a nonreinforcing filler. In other studies where fundamental phenom-

ena that are not readily accessible with powdered ammonium perchlorate are important, glass spheres have been used as a model for the oxidizer. In an effort to improve adhesion, surface treatments have been applied to the filler. For example, in an investigation of the tear strength and tensile strength of a model glass-filled polybutadiene (Dreyfuss, et al., 1980), positive effects on mechanical properties were observed as a result of surface treatment with certain silanes. These effects correlated well with those reported by Markin and Williams (1974) for silane treated ammonium perchlorate particles and with predictions based on adhesion studies with flat plates. The studies with glass spheres also revealed that mechanical properties are significantly influenced by the size of the particles. This paper is an updated literature survey of the effect of nonreinforcing fillers on the properties of composites and a comparison of the literature results with new results from our laboratory.

Following Bueche (1962) a "reinforcing" filler is defined as a filler which raises the modulus while still maintaining the rubber-like qualities of the base material and which at the same time increases the strength of low-strength rubbers. A "nonreinforcing" filler is one which does not have these effects. For purposes of this paper it is assumed that nonreinforcing fillers do not form molecular bonds with the rubber even if the rubber wets the filler surface. Accordingly, surface treated particles carrying surface

functional groups capable of bonding to the rubber are excluded from the present discussion.

## RESULTS AND DISCUSSION

Mechanical properties of filled elastomers have been studied extensively as a function of the concentration of glass beads and other nonreinforcing filler particles (e.g. Bills et al. 1960; Schwarzl et al. 1965; Alter, 1965; Nielsen, 1966 and 1974; Evram and Nottin, 1975). Properties of filled plastic materials have also been examined (e.g. Nicolais and Narkis, 1971; Migliaresi et al., 1971; Broutman and Sahu, 1971, Leidner and Woodhams, 1976). The results of the studies of plastic materials complement those with elastomers. Experimental data on the effect of particle size of "nonreinforcing" fillers on mechanical properties of composites are more limited (Schwarzl et al., 1965; Alter, 1965, Nielsen, 1974; Leidner and Woodhams, 1976). Depending on the system and property being studied, conclusions range from lack of effect of particle size on mechanical properties of the composite (Bills et al., 1960; Schwarzl et al., 1965), to an inverse variation of the properties with size (Alter, 1965), or its square root (Leidner and Woodhams, 1976). Most of these studies were made with particles within a narrow particle size range. Eckstein and Dreyfuss (1982) expanded the size range to include particles with a mean diameter as large as 1000  $\mu\text{m}$  and as small as 25  $\mu\text{m}$ .



Comparison of results will be made property by property in the following.

### Modulus

The increase in the Young's modulus of a composite as a function of the volume fraction of the filler, can be predicted from the Smallwood-Guth-Einstein relation (Kraus, 1965):

$$E = E_0 (1 + 2.5 V_F + 14.1 V_F^2) \quad (\text{eq. 1})$$

where  $E$  is the modulus of the filled rubber,  $E_0$  is the modulus of the rubber matrix and  $V_F$  is the volume concentration of the filler. No dependence of the modulus on particle size is predicted. Accordingly, Schwarzl et al. (1965) found that shear moduli of NaCl filled polyurethane rubber in the glassy and rubbery states were independent of filler size. In contrast, shear moduli increased considerably with filler content. Evrand and Nottin (1975) observed that at low deformations the reinforcing properties of spherical particles in an elastomeric matrix were not related to particle size.

The values of Young's modulus reported by Eckstein and Dreyfuss (1982) for filled polybutadiene were in the same range as the theoretical one calculated from equation 1. However, contrary to theoretical predictions and the experimental observations cited above they found a small but systematic variation with particle size. This observation is in agreement with Alter's who noted a linear dependence of relative modulus on reciprocal particle size for fillers less than 0.2  $\mu\text{m}$  in radius. More will be said about this below when the moduli are compared to swelling ratios on the same samples.

### Swelling ratios

Swelling is equivalent in many respects to a three dimensional stretching of the elastomer. Although several theoretical treatments are available (Bills and Salcedo, 1961; Kraus, 1963; Fedors and Landel, 1966), the significance of swelling measurements of composites is not fully understood.

Kraus (1963) developed a theory for the swelling of filler-reinforced vulcanizates. His theory assumes that swelling of a crosslinked elastomer is restricted at the filler-rubber interface due to adhesion between the filler and the rubber. This theory predicts that the swelling ratio decreases with increased loading according to the following relation:

$$v_{ro}/v_r = 1 - [3c(1 - v_{ro}^{-1/3}) + v_{ro} - 1]V_F/(1 - V_F) \quad (\text{eq. 2})$$

where  $v_r$  is the volume fraction of rubber in the swollen rubber phase,  $v_{ro}$  is the same quantity referred to an otherwise analogous, unfilled vulcanizate,  $V_F$  is the volume fraction of the filler, and  $c$  is a parameter depending on the filler, but independent of  $V_F$  and  $v_{ro}$ . According to Kraus  $c$  is a measure of the ability of the filler to restrict swelling of the binder. If  $c = 0$ , there is no adhesion between the filler and the binder and then, the filler does not restrict swelling. According to Kraus the volume swelling  $Q$  is then given by:

$$Q = v_r^{-1} = (q_o^3 - V_F)/(1 - V_F) = (v_{ro}^{-1} - V_F)/(1 - V_F) \quad (\text{eq. 3})$$

where  $q_0$  is the linear swelling coefficient of the rubber,  $v_r$  is the apparent volume fraction of rubber in the swollen gel and  $v_{ro}$  is its true value, equal to the inverse swelling ratio of the analogous gum vulcanizate. Kraus reported that the theory was obeyed for a large amount of experimental data on carbon blacks, in four different rubbers, with several vulcanizing systems, in five solvents and over a wide range of crosslinking. For these systems the average value of  $c$  was 1.17. In the few cases where the theory was not obeyed, Kraus concluded that the adhesion between the filler and the binder was poor and observed values of  $c$  well below 1.

Dick, et al. (1975) determined swelling ratios as a function of filler content for urethane rubbers containing 50-80 weight %  $NH_4ClO_4$ . In some cases the filler was treated with agents that varied the degree of adhesion between the filler and the matrix. They found that the swelling behavior followed the relation derived by Kraus. They further demonstrated that as shown in Figure 1, the nature of the variation of the swelling ratio with loading changed with the degree of adhesion between the filler and the matrix. A solvent dependence was also found.

Fedors and Landel (1966) found that the swelling ratio of a composite from glass beads and styrene butadiene rubber (SBR) decreased slowly as loading of the glass beads was increased. They supposed that since the SBR is essentially nonpolar in nature, the glass beads did not interact strongly with the SBR binder, i.e. that  $c = 0$  in Kraus' equation. In order to explain the above decrease, they concluded tentatively that the decrease was the result of particle agglomeration or clustering. To fit Kraus' theory a value of  $c = 0.33$  was required.

Bills and Salcedo (1961) concluded that the swelling ratio is the same with and without filler and does not vary with loading. Their treatment was based on two assumptions; namely, (1) the adhesion between filler and binder was poor so that the binder-filler bond releases on swelling and (2) the swelling of the binder,

with and without filler, is the same. They prepared samples in which concentration of glass filler in a polyurethane binder was controlled by casting into tube containers and allowing the filler to settle before curing. Their data seemed to justify their assumptions. More recently Eckstein and Dreyfuss (1982) have noted that their data can equally well be interpreted as showing a slow decrease of swelling ratio with increasing loading. Unfortunately, Bills and Salcedo (1961) based their conclusion primarily on pairs of data where one member of the pair was the "unfilled" polyurethane and the other was filled. For most of these pairs the swelling ratio for the filled sample was lower. The "unfilled" polyurethane was taken from the top part of their tube. The one set of data that has four data points shows the slow decrease noted above if the "unfilled" value is ignored. (See Eckstein and Dreyfuss, 1982).

Eckstein and Dreyfuss (1982) determined swelling ratios of polybutadiene filled with glass beads of different sizes and at different loadings. Their swelling ratios decreased slowly as the loading was increased for every particle size examined. They analyzed their results in terms of the resulting distance between neighboring particles. This distance is given by (Rehner, 1965):

$$D = d_f [\pi/6v_f]^{1/3} - 1] \quad (\text{eq. 4})$$

assuming that an elastic medium contains a volume fraction  $V_f$  of particles of diameter  $d_f$  arranged in a cubic lattice. The mean distances between two particles thus calculated are given in Table I as a function of the mean glass sphere diameter. Eckstein and Dreyfuss noted that the swelling ratios initially decreased with particle size, had a minimum value for samples containing spheres of about 100  $\mu\text{m}$  in diameter and then increased again. Plots of swelling ratio as a function of particle separation distance showed a systematic shift of the minimum for the curves with increasing loading of the filler; the lower the loading, the greater the distance at which the minimum occurred. Thus it appears that clustering as proposed by Landel and Fedors cannot explain the decrease of swelling ratio observed with increasing loading. It has previously been noted that the adhesion between polybutadiene and glass is unexpectedly high (Dreyfuss, et al., 1980; Runge and Dreyfuss, 1979; Wong, 1979). Since SBR also contains polymerized butadiene units, the same is probably true for SBR. Thus it seems that these data are consistent with those of Dick, et al. and in agreement with the theory of Kraus. A value  $c = 0$  is probably not a valid assumption for describing the interaction between glass and SBR.

Eckstein and Dreyfuss (1982) also observed that the swelling ratio of glass-filled polybutadiene showed a complex dependence on particle size at constant loading. The dependence was similar to that already described for swelling ratio on interparticle distance. Alter (1965) has suggested analyzing data based on particle size in terms of the surface to volume ratio of the particle. This reduces

to an analysis in terms of the reciprocal of the diameter of the particle. When the data are plotted in this way as shown in Figure 2 and compared with corresponding modulus data plotted in the same way and also shown in Figure 2, the dependence on particle size becomes clearer. The swelling ratio curve shows an inverse relationship to the other curve at all loadings. The fact that there is an inflection in the curves for both modulus and swelling ratio for particles about  $143\text{ }\mu\text{m}$  in diameter suggests that different factors are influencing properties above and below this size of filler. For example, above  $143\text{ }\mu\text{m}$  it is possible that the effect of surface attachments becomes more pronounced as the particles get smaller and for any given loading the surface area increases. Below  $143\text{ }\mu\text{m}$  the increasing effect of surface attachments as particles get smaller might be overshadowed by interactions in volume elements surrounding the particles. (See Figure 3) Such interactions would be more pronounced at the short distances between particles arising either from high loadings or from the smallest particles at constant loading. Alternatively, particle sizes below  $143\text{ }\mu\text{m}$  may be in the range of inherent flaw sizes for the system, so that the size effect disappears. Flaw size effects will be explored further below.

In view of the foregoing discussion about all the factors that can influence the swelling behavior of composites, it is clear that equilibrium swelling measurements are sufficiently ambiguous to preclude calculation of reliable values of crosslink density.

### Fracture energy

The tear quality of a rubber can be expressed by a characteristic energy which is related to the energy stored in a highly strained zone at the tip of a growing tear: as the tip grows, most of the energy is dissipated irreversibly as heat. This tearing energy varies with the nature of the rubber and of the filler. Dreyfuss, Gent, and Williams (1980) noted that the intrinsic tear strength of glass-bead-filled matrices with particles of 150  $\mu\text{m}$  or less was not much different from that of the unfilled matrix. They attributed the slight enhancement observed with filled samples to a deviation of the tear path from a straight line caused by the presence of glass beads in the material. Such a deviation should result in a rougher tear path and a correspondingly higher tear strength. The enhancement of tear strength in the presence of such small particles might also result from increasing importance of a surface energy term as expressed by the relationship (Lange, 1972):

$$\gamma = \gamma_0 + L/D \quad (\text{eq. 5})$$

where  $\gamma$  denotes the fracture surface energy of the composite,  $\gamma_0$  the fracture surface energy of unfilled matrix,  $L$  the line tension of the crack front and  $D$  the distance between the particles. At a given volume fraction of the filler, the interparticle distance becomes smaller as the size of the glass beads decreases (see Table I). It follows, thus, from equation 5 that highest fracture surface energy should be obtained with the finest particles. Broutman and Sahu (1971) attributed the enhancement of

fracture energy with increasing glass beads volume content in epoxy and polyester resins to a similar effect. Also, a study by Mullins(1963)indicated the importance of fine-particle fillers for high fracture energy.

In a study with glass beads with diameters ranging from 25 to 1000  $\mu\text{m}$  Eckstein and Dreyfuss (1982) observed that the mode of fracture was a function of the particle size of the filler. With the largest particles the tear path often travelled from bead to bead. For small particles the data were in agreement with the above and clearly demonstrated that the smallest particles were the most effective in increasing tear strength of the composites. The tear strength of compounds containing the smallest particles (25  $\mu\text{m}$ ) increased by about 50% compared to that of unfilled polybutadiene, while that of the composites containing larger glass beads increased by only 25%.

In presence of larger inclusions, the smaller increase in fracture energy resulted from the irregularity of the tear path and increase in the effective diameter,  $C$ , of the tip of the tear. The effective diameter,  $C$ , is defined by (Dreyfuss, Gent, and Williams, 1980):

$$C = T/2kU_b \quad (\text{eq. 6})$$

where  $T$  is the tear energy,  $U_b$  the strain energy per unit volume and  $k$  is a numerical quantity, to which a value of 2 was assigned for moderate deformations. The stored strain energy,  $U_b$ , can be calculated from the area under the stress-strain curve. The calculated values of the effective diameter,  $C$ , of the edge flaw from which fracture initiates, taken from the data of Eckstein



and Dreyfuss (1982), are given in the last column of Table I. When the particle diameter is in the range of 14-35  $\mu\text{m}$ , the apparent size of the flaw is the same as that of the unfilled material. In the range of sizes between 60 and 225  $\mu\text{m}$ , the effective size of the flaw seems to be of the same order of magnitude as the diameter of the largest particles present. With the largest beads, the calculated flaw size (528  $\mu\text{m}$ ) is much smaller than the largest particle present (1411  $\mu\text{m}$ ). Instead, it correlates rather well with the mean distance between particles (484  $\mu\text{m}$ ) shown in the table. Perhaps with very large particles the flaw size is determined by the average distance between particles instead of by the diameter of the bead. The observed deviation of the crack front around the largest spheres ( $\sim 1000$   $\mu\text{m}$ ) which travels from one bead to another in a straight line supports such a possibility.

#### Mechanical hysteresis ratio, H

Andrews (1961 and 1963) has pointed out that the greater the hysteresis, the smaller the value of stress concentration at the tip of the tear. Hysteresis arises also from possible slippage between the rubber and the filler surfaces. Gent (1980) predicted that the mechanical hysteresis ratio, H, given by

$$H = 3V_F/\pi \quad (\text{eq. 7})$$

and caused by debonding of the rubber from a spherical inclusion, should be independent of particle size and proportional to the volume fraction,  $V_F$ , of the particles in the composite.

Eckstein and Dreyfuss (1982) found that the hysteresis ratio does depend on particle size. The H value increased with particle size up to about 100  $\mu\text{m}$  and then decreased slightly with further increase in the filler size. In each case the maximum amount of energy dissipated was lower than the theoretically predicted value from equation 7. As in the case of swelling ratios, this can be attributed to interactions of strain fields around each particle, which becomes more significant when the separation distance between particles is smaller than their diameter. As predicted by Gent's (1980) theory, the low hysteresis ratio obtained in compounds consisting of glass spheres smaller than 100  $\mu\text{m}$  might be caused by rupture of the matrix near the inclusion instead of detachment of the matrix from the inclusion. The slight decrease in hysteresis ratio with particles larger than 250  $\mu\text{m}$  might be caused by the presence of two competing modes of failure: dewetting and matrix rupture. Micrographs of torn surfaces in compounds containing 1000  $\mu\text{m}$  spheres are consistent with these mechanisms.

#### Stress and strain at break

Tensile strength and elongation are the most widely studied properties of filled composites (e.g. Bills et al., 1960; Schwarzl et al. 1965; Nielsen, 1974; Smith, 1959; Nicolais and Narkis, 1971). According to the reports, rigid fillers cause a comparatively small decrease in tensile strength and a dramatic decrease in elongation at break.

Reports of experimental observations on the effect of particle size on stress-strain properties of filled elastomers are few and do not agree well with each other. Oberth (1967) and others (Cohan, 1950,; Cohan, 1947; Payne, 1966, Gehman, 1965) found little effect of particle size on breaking stress. Alter (1965) has reviewed much of the data. He states that up to particle radii of 0.2  $\mu\text{m}$ , relative stress and elongation at break are functions of the reciprocal of the filler particle size. According to Alter (1965) the reciprocal relationship may be viewed as a dependence on the surface area to volume ratio for the filler. At larger particle sizes, according to Alter, there was too much scatter to reach any conclusions. Schwarzl et al. (1965), who used NaCl as inert filler in polyurethane, found that deformation at large strains was dependent on particle size but at low strains particle size dependence was not important and only filler content had a significant effect on mechanical properties. The results of Eckstein and Dreyfuss (1982) and the data of Schwarzl et al. (1965) are compared in Figures 4 and 5, where following Alter, relative stress at break,  $\sigma_b/\sigma_b^\circ$  and relative elongation at break,  $e_b/e_b^\circ$  are plotted versus reciprocal particle size. Here  $e_b^\circ$  and  $\sigma^\circ$  refer to the unfilled elastomer and  $e_b$  and  $\sigma_b$  refer to the filled elastomer.

The data in Figures 4 and 5 are not scattered. The results are clearly systematic functions of both loading and particle size. As loading decreases,  $\sigma_b/\sigma_b^\circ$  converges. The  $\sigma_b/\sigma_b^\circ$  scale for the polybutadiene has been expanded compared to that for the polyurethane data. Then it is apparent that in contrast to the

polyurethane data where the loading lines are parallel over the whole range of particle sizes, the lines for the largest fillers used in polybutadiene have different slopes. The larger particles have a bigger effect in reducing relative breaking stress in both systems. However the pronounced inflection that is apparent in both sets of curves occurs at a different mean diameter. The values are 143  $\mu\text{m}$  and 70  $\mu\text{m}$  for the polybutadiene and polyurethane systems, respectively. One possible explanation of the significance of these values can be given in terms of flaw sizes, as discussed in the section on tear strength. The inflection in the relative mechanical property curves (Figures 2 and 4) may be related to inherent flaws in the rubbery matrix. If so, as shown in Figure 5, the inherent flaw size varies with the system.

The shape of the relative breaking elongation versus particle size curves are quite different from corresponding ones for the relative breaking stress. There is a systematic variation with reciprocal particle size and loading but the nature of the variation is different in the two systems.

In 1976 Leidner and Woodhams developed a theoretical relationship which relates the strength at break of a composite containing spherical fillers to the size, volume fraction and interfacial adhesion between the filler and the matrix. They showed that the relative strength of a composite filled with a spherical filler is inversely proportional to the square root of the sphere diameter. Efforts to fit the data of Eckstein and Dreyfuss (1982) to this theory have been unsuccessful.

Evrard and Nottin's (1975) study on reinforcement of butadiene-styrene rubber by spherical particles (30, 75, 150 $\mu$  in diameter) indicated that at high deformations the reinforcing potential increased as the particle size of the filler decreased, and as the adhesion to the matrix increased.

Nielsen (1966) suggested the following equation relating relative elongation at break and filler concentration in the case of perfect adhesion between polymer and filler particles:

$$e_b/e_b^0 = 1 - v_F^{1/3} \quad (\text{eq. 8})$$

Since Dreyfuss et al. (1980), Runge and Dreyfuss (1979), Wong (1979) and Eckstein and Dreyfuss (1982) had observed unexpectedly large adhesion of polybutadiene to glass, and as discussed above, the swelling ratio data was also consistent with significant adhesion between the glass bead filler and polybutadiene, an attempt was made to plot the results of Eckstein and Dreyfuss (1982) according to this equation. In Figure 6 the volume fraction of glass in the elastomer is plotted as a function of the relative strain for three different sizes of the filler: 60, 145 and 225  $\mu$ m in diameter. The compounds consisting of small beads (60  $\mu$ m) showed higher relative strain, while the larger beads produced similar but lower relative strain values than those predicted from equation 8. With a decrease of the glass volume fraction, the relative strain converged.

Since the right-hand side of equation 8 has a fixed value which depends upon the amount of filler present in the composite, a deviation, positive or negative, of the quantity on the left-hand side from the fixed value, would imply good or bad

adhesion, respectively. The plot of the amount of deviation,  $\delta$ , of the measured relative elongation at break from the theoretical value (namely,  $\delta = e_b/e_b^0 - (1 - V_F^{1/3})$ ) as a function of particle size showed an inflection in the curve, occurring at a filler diameter of about 80  $\mu\text{m}$ . The position of the inflection was independent of the volume fraction of the filler. A plot of the same deviation as a function of the reciprocal of particle size showed a linear dependence as the particle size increased. The deviation, and therefore the adhesion strength, decreased (see Figure 7).

#### SUMMARY AND CONCLUSIONS

Mechanical properties of filled elastomers are a complex function of loading (separation distance), particle size (surface/volume) and the system being studied. It has been shown that relative modulus, relative breaking elongation and stress, and swelling ratio are functions of the reciprocal size of the filler up to particle size of about 140  $\mu\text{m}$ . With filler particles of larger diameter the influence on those properties is smaller. When the distance between particles is smaller than their size, the interactions in the volume surrounding the particles may become the dominant variable.

It is noteworthy that a similar complex dependence of mechanical properties on particle has been reported for alloys strengthened by dispersion of hard particles (Preston and Grant, 1961).

#### ACKNOWLEDGEMENT

This work was supported in part by a research grant from the Office of Naval Research.

- Ahagon, A. and Gent, A. N., J. Polym. Sci: Polym. Phys. Ed., 1975, 13, 1285.
- Andrews, E. H., J. Appl. Phys., 1961, 32, 542.
- Andrews, E. H., Rubber Chem. Technol., 1963, 36, 325.
- Alter, H. J. Appl. Polym. Sci., 1965, 9, 1525.
- Bills, K. H., Jr., Sweeny, K. H. and Salcedo, F. S., J. Appl. Polym. Sci., 1960, 4, 259.
- Bills, K. H., Jr. and Salcedo, F. S., J. Appl. Phys., 1961, 32, 2364.
- Broutman, L. Y. and Sahu, S., Mater. Sci.: Eng., 1971, 8, 98.
- Bueche, F. "Physical Properties of Polymers; Interscience: New York, 1962.
- Cohan, L., India Rubber World, 1947, 117, 344.
- Cohan, L., Rubber Chem. Technol., 1950, 23, 635.
- Dick, R., Mavel, G., Mankowski-Favelier, R., 1975, Colloq. Int. C.N.R.S., 231, 165.
- Dreyfuss, P., Eckstein, Y., Lien, Q.-S. and Dollwet, H. H., J. Polym. Sci., Polym. Lett. Ed., 1981, 19, 427.
- Dreyfuss, P., Gent, A. N. and Williams, J. R., J. Polym. Sci., Polym. Phys. Ed., 1980, 18, 2135.
- Eckstein, Y., Dreyfuss, P., J. Polym. Sci., Polym. Phys. Ed., 1982, 20, 49.
- Evrard, G., Nottin, J. P., Colloq. Int. C.N.R.S., 1975, 231, 271.
- Fedors, R. F., and Landel, R. F., J.P.L. Space Programs Summ., 1966, 37-40, IV, 80.
- Gehman, S. D., in: Reinforcement of Elastomers, Kraus, G., Ed., Interscience: New York, 1965; Chap. 2, p 23.
- Gent, A. N., J. Mater. Sci., 1980, 15, 2884.
- Granstein, D. L., and Williams, H. J., J. Appl. Polym. Sci., 1974, 18, 1.
- Kraus, G., J. Appl. Polym. Sci., 1963, 7, 861.

- Kraus, G., in "Reinforcement of Elastomers", Kraus, G., Ed., Interscience : N.Y., 1965; Chap 4, p 125.
- Lange, F. F., Am. Ceram. Soc. Bull., 1970, 49, 390.
- Leidner, J., and Woodhams, R. T., 1976, 11-st Ann. Techn. Conf., Reinforced Plastics/Composites Institute, SPI, sec. 8F, 1.
- Markin, C., and Williams, H. L., J. Appl. Polym. Sci., 1974, 18, 21.
- Migliaresi, C., Nicolais, L., Nicodeme. L., and DiBenedetto, A. T., Polymer Composites, 1971, 2, 29.
- Mullins, L., in The Chemistry and Physics of Rubberlike Substances, L. Bateman ed., Maclaren, London, 1963, p 301.
- Nicolais, L. and Narkis, M., Polym. Eng. Sci., 1971, 11, 194.
- Nielsen, L. E., J. Appl. Polym. Sci., 1966, 10, 97.
- Nielsen, L. E., in: Mechanical Properties of Polymers and Composites, Dekker : New York, 1974, vol. 2 p 413.
- Oberth, A. E., Rubber Chem. Technol., 1967, 40, 1337.
- Payne, A. R. in: Composite Materials, L. Holliday, Ed., Elsevier: New York, 1966, Chap. 7, p 23.
- Preston, O., and Grant, N. J., Trans. AIME, 1961, 221, 612.
- Rehner, J., Jr., in "Reinforcement of Elastomers", Kraus, G., Ed., Interscience : New York, 1965; chap. 5, p 153.
- Runge, M. L., and Dreyfuss, P., J. Polym. Sci. Polym. Chem. Ed., 1979, 17, 1067.
- Schwarz, W. W., and Lowrey, R. D., J. Appl. Polym. Sci., 1967, 11, 533.
- Schwarzl, F. R., Bree, H. W., and Nederveen, C. Y., in: "Proceedings, Fourth International Congress on Rheology," Lee, E. H., Ed., Interscience : New York, 1965; Part 3, p 241.
- Smith, T. L., Trans. Soc. Rheol., 1959, 3, 113.
- Wong, S. G., J. Rubber Res. Inst., 1979, Malays., 27, 24.



TABLE I

Interparticle Separation Distance and Edge Flaw  
as a Function of Particle Size<sup>a</sup>

Measured diameter ( $\mu\text{m}$ )	Mean diameter ( $\mu\text{m}$ )	Mean Separation distance ( $\mu\text{m}$ )	Edge flaw, C ( $\mu\text{m}$ )
No glass added	-	-	123
14-35	25	12	153
30-90	60	29	278
80-220	145	70	330
90-355	225	109	364
855-1411	1000	484	528

a) Volume fraction of glass,  $V_F = 0.16$

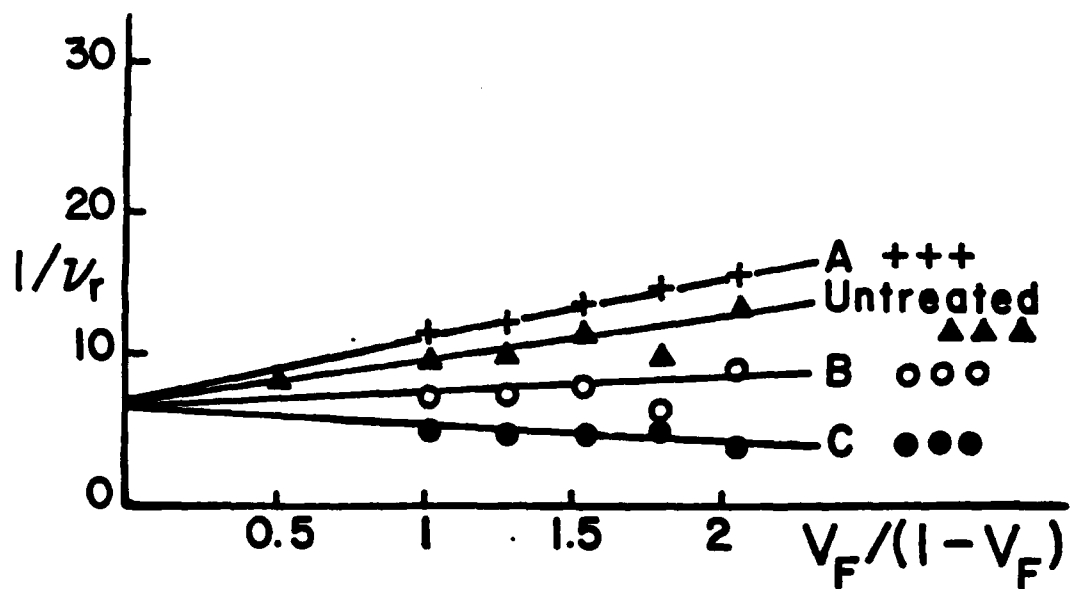


Figure 1. Variation of the swelling ratio in benzene of urethane rubbers filled with  $\text{NH}_4\text{ClO}_4$ , as a function of filler content. A, B and C are treated fillers in which the adhesion between the filler and the matrix varies in the order  $A < B < C$ . Dick, et al. (1975).

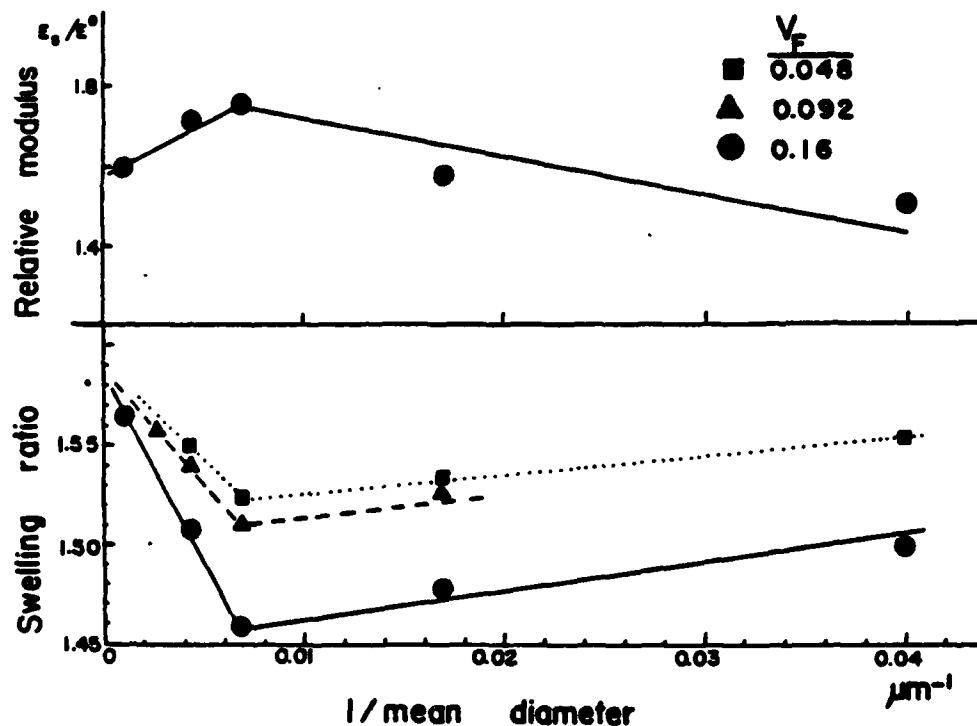


Figure 2. Relative modulus and swelling ratio as a function of reciprocal of the mean diameter of the glass particles in polybutadiene at the volume fraction  $V_F$  indicated in the figure.  $E$  and  $E_0$  are moduli of the filled and unfilled rubber, respectively. (The data could equally well be represented by smooth curves) Eckstein and Dreyfuss (1982).

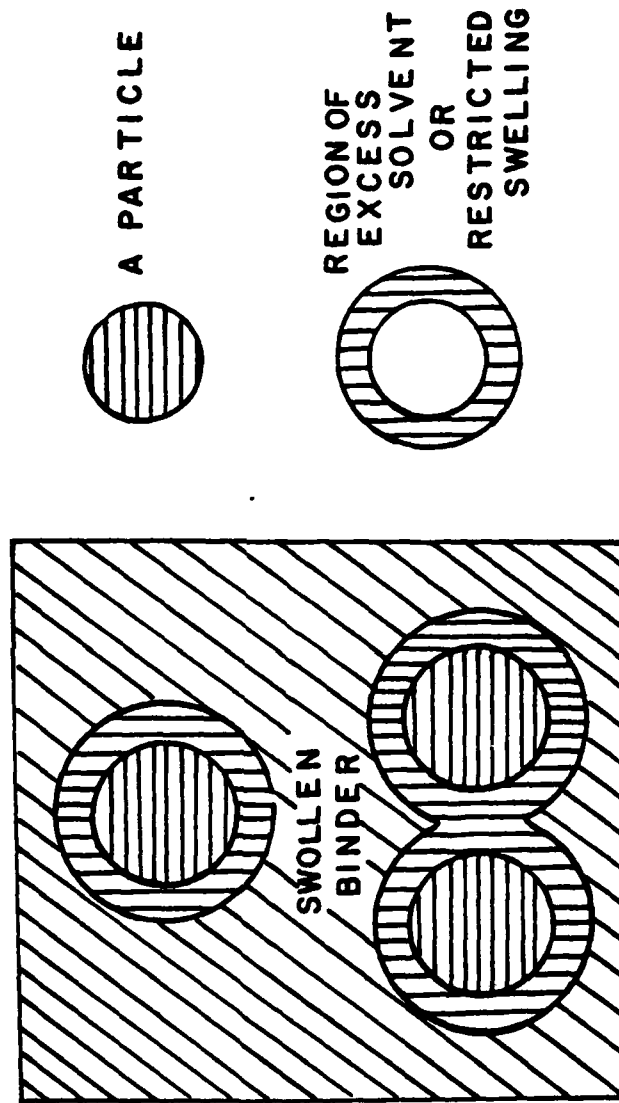


Figure 3. Schematic representation of a swollen composite showing an isolated particle with no interaction of the surrounding volume elements and two particles in close enough proximity, so that interactions can occur in the overlapping volume elements.

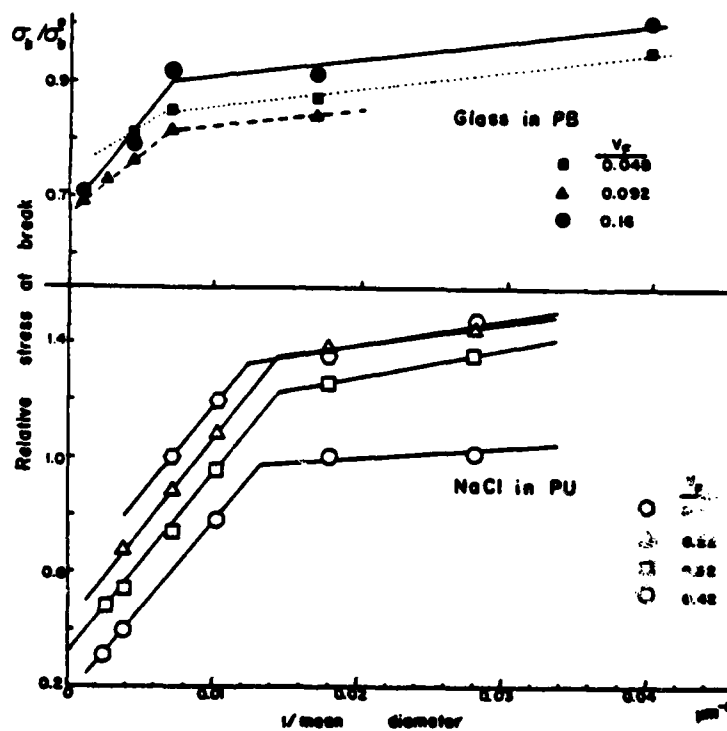


Figure 4. Relative stress at break as a function of mean diameter of glass beads in polybutadiene (PB) and of salt particles in polyurethane (NaCl in PU).  $\sigma_b$  and  $\sigma_b^0$  are the tensile strength at break of the filled and unfilled systems. Eckstein and Dreyfuss (1982).

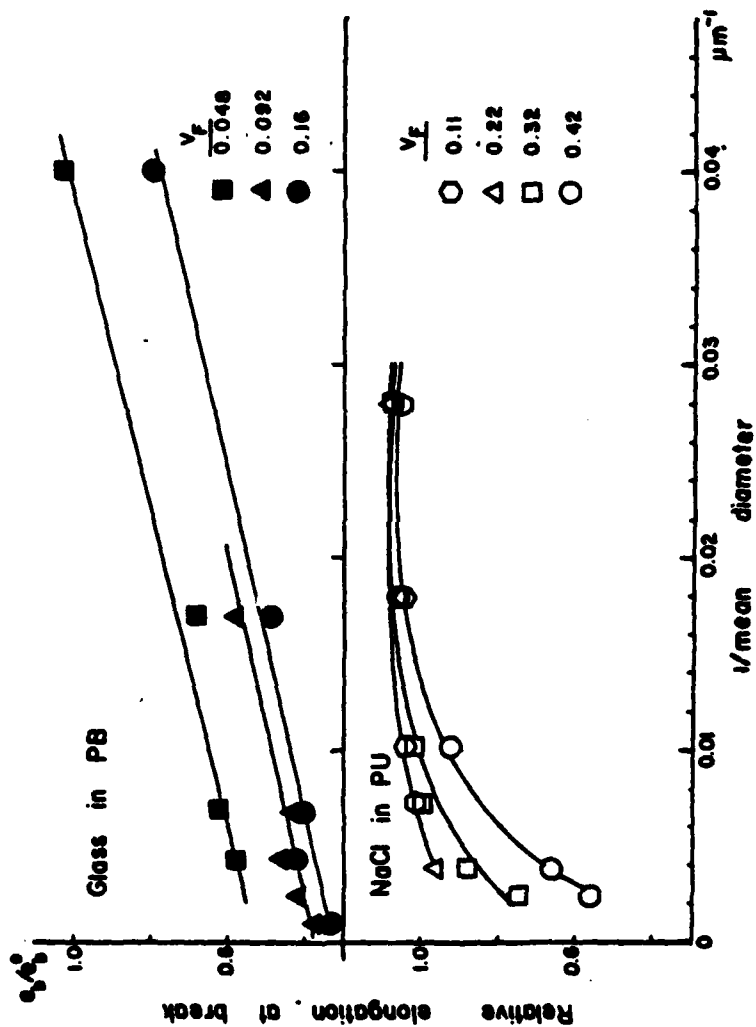


Figure 5. Relative elongation at break as a function of mean diameter of glass beads in polybutadiene (PB) and of salt particles in polyurethane (NaCl in PU).  $e_b$  and  $e_b^0$  are the elongations at break of the filled and unfilled systems. Eckstein and Dreyfuss (1982).

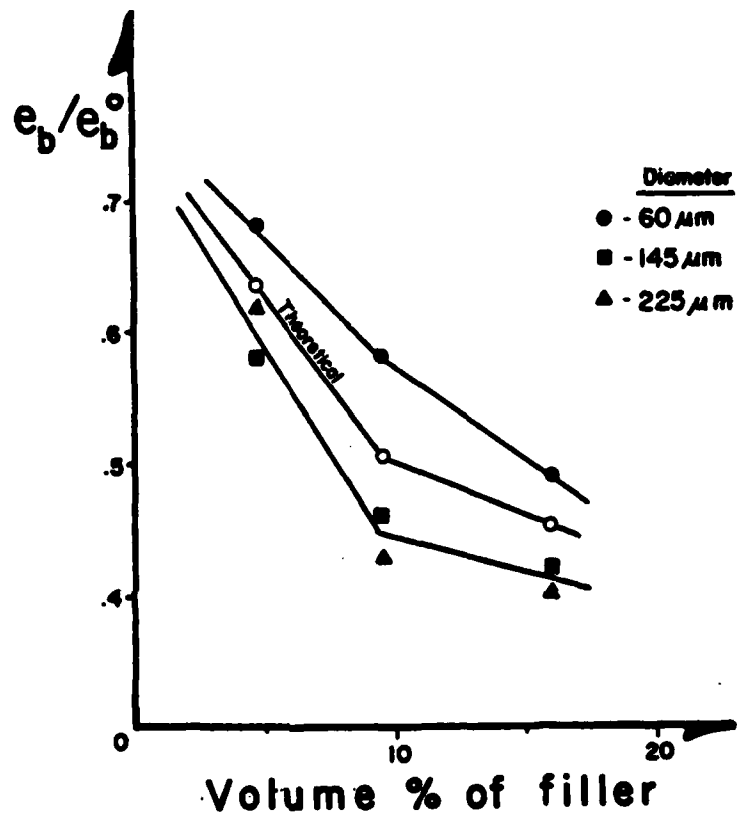


Figure 6. Theoretical and experimental curves for the elongation at break as a function of volume fraction of glass beads in polybutadiene, for the cases of spheres of 60, 145 and 225  $\mu\text{m}$  in diameter.

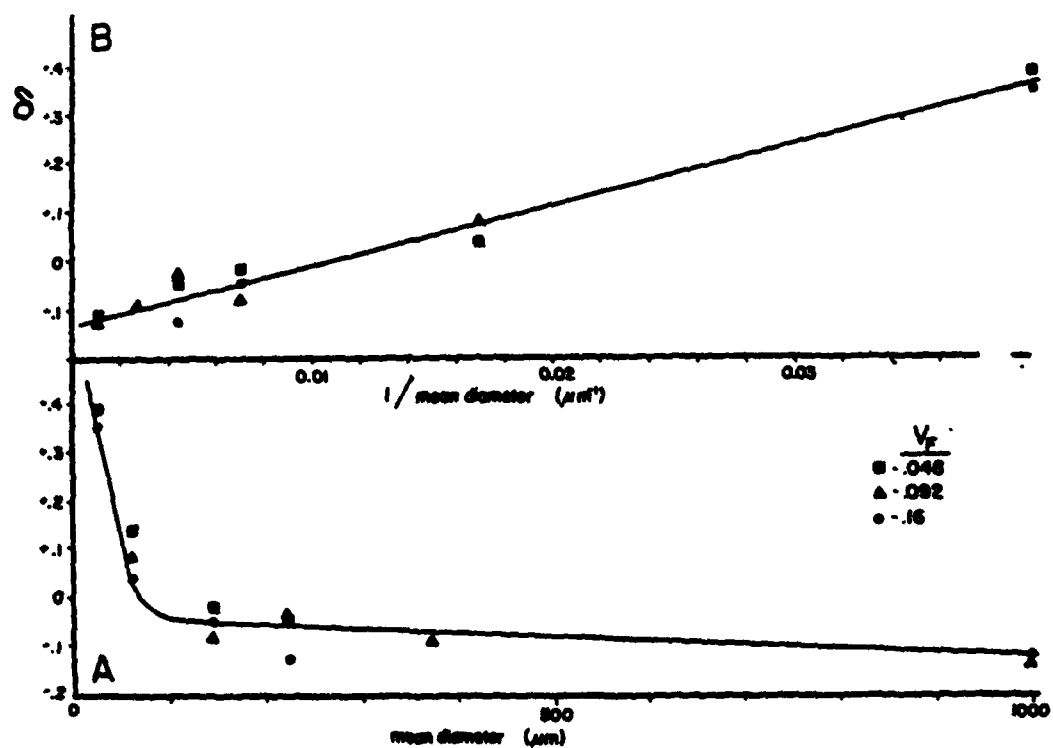


Figure 7. Plot of the amount of deviation  $\delta$ , of the measured value  $(e_b/e_b^*)_{\text{meas}}$  from the theoretical  $(e_b/e_b^*)_{\text{theor}} = 1 - V_F^{1/3}$ , so that  $\delta = (e_b/e_b^*)_{\text{meas}} - (e_b/e_b^*)_{\text{theor}}$ , as a function of A) particle size, B) reciprocal of particle size.



DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. L.V. Schmidt Assistant Secretary of the Navy (R,E, and S) Room 5E 731 Pentagon Washington, D.C. 20350	1	Dr. F. Roberto Code AFRPL MKPA Edwards AFB, CA 93523	1
Dr. A.L. Slafkosky Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1	Dr. L.H. Caveny Air Force Office of Scientific Research Directorate of Aerospace Sciences Bolling Air Force Base Washington, D.C. 20332	1
Dr. Richard S. Miller Office of Naval Research Code 413 Arlington, VA 22217	10	Mr. Donald L. Ball Air Force Office of Scientific Research Directorate of Chemical Sciences Bolling Air Force Base Washington, D.C. 20332	1
Mr. David Siegel Office of Naval Research Code 260 Arlington, VA 22217	1	Dr. John S. Wilkes, Jr. FJSRL/NC USAF Academy, CO 80840	1
Dr. R.J. Marcus Office of Naval Research Western Office 1030 East Green Street Pasadena, CA 91106	1	Dr. R.L. Lou Aerojet Strategic Propulsion Co. P.O. Box 15699C Sacramento, CA 95813	1
Dr. Larry Peebles Office of Naval Research East Central Regional Office 666 Summer Street, Bldg. 114-D Boston, MA 02210	1	Dr. V.J. Keenan Anal-Syn Lab Inc. P.O. Box 547 Paoli, PA 19301	1
Dr. Phillip A. Miller Office of Naval Research San Francisco Area Office One Hallidie Plaza, Suite 601 San Francisco, CA 94102	1	Dr. Philip Howe Army Ballistic Research Labs ARRADCOM Code DRDAR-BLT Aberdeen Proving Ground, MD 21005	1
Mr. Otto K. Heiney AFATL - DLDL Elgin AFB, FL 32542	1	Mr. L.A. Watermeier Army Ballistic Research Labs ARRADCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005	1
Mr. R. Geisler ATTN: MKP/MS24 AFRPL Edwards AFB, CA 93523	1	Dr. W.W. Wharton Attn: DASMZ-RKL Commander U.S. Army Missile Command Redstone Arsenal, AL 35898	1

## DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. R.G. Rhoades Commander Army Missile Command DRSMI-R Redstone Arsenal, AL 35898	1	Dr. E.H. Debutts Hercules Inc. Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. W.D. Stephens Atlantic Research Corp. Pine Ridge Plant 7511 Wellington Rd. Gainesville, VA 22065	1	Dr. James H. Thacher Hercules Inc. Magna Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. A.W. Barrows Ballistic Research Laboratory USA ARRAACOM DRDAR-BLP Aberdeen Proving Ground, MD 21005	1	Mr. Theodore M. Gilliland Johns Hopkins University APL Chemical Propulsion Info. Agency Johns Hopkins Road Laurel, MD 20810	1
Dr. C.M. Frey Chemical Systems Division P.O. Box 358 Sunnyvale, CA 94086	1	Dr. R. McGuire Lawrence Livermore Laboratory University of California Code L-324 Livermore, CA 94550	1
Professor F. Rodriguez Cornell University School of Chemical Engineering Olin Hall, Ithaca, N.Y. 14853	1	Dr. Jack Linsk Lockheed Missiles & Space Co. P.O. Box 504 Code Org. 83-10, Bldg. 154 Sunnyvale, CA 94088	1
Defense Technical Information Center DTIC-DDA-2 Cameron Station Alexandria, VA 22314	12	Dr. B.G. Craig Los Alamos National Lab P.O. Box 1663 MSP/DOD, MS-245 Los Alamos, NM 87545	1
Dr. Rocco C. Musso Hercules Aerospace Division Hercules Incorporated Alleghany Ballistic Lab P.O. Box 210 Washington, D.C. 21502	1	Dr. R.L. Rabie WX-2, MS-952 Los Alamos National Lab. P.O. Box 1663 Los Alamos NM 37545	1
Dr. Ronald L. Simmons Hercules Inc. Eglin AFATL/DL0L Eglin AFB, FL 32542	1	Dr. R. Rogers Los Alamos Scientific Lab. P.O. Box 1663 Los Alamos, NM 87545	1

## DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. R. Brown Naval Air Systems Command Code 330 Washington, D.C. 20361	1	Dr. J. Schnur Naval Research Lab. Code 6510 Washington, D.C. 20375	1
Dr. H. Rosenwasser Naval Air Systems Command AIR-310C Washington, D.C. 20360	1	Mr. R. Beauregard Naval Sea Systems Command SEA 64E Washington, D.C. 20362	1
Mr. B. Sobers Naval Air Systems Command Code 03P25 Washington, D.C. 20360	1	Mr. G. Edwards Naval Sea Systems Command Code 62R3 Washington, D.C. 20362	1
Dr. L.R. Rothstein Assistant Director Naval Explosives Dev. Engineering Dept. Naval Weapons Station Yorktown, VA 23691	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, PA 19112	1
Dr. Lionel Dickinson Naval Explosive Ordnance Disposal Tech. Center Code D Indian Head, MD 20640	1	Dr. H.G. Adolph Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1
Mr. C.L. Adams Naval Ordnance Station Code PM4 Indian Head, MD 20640	1	Dr. T.D. Austin Naval Surface Weapons Center Code R16 Indian Head, MD 20640	1
Mr. S. Mitchell Naval Ordnance Station Code 5253 Indian Head, MD 20640	1	Dr. T. Hall Code R-11 Naval Surface Weapons Center White Oak Laboratory Silver Spring, MD 20910	1
Dr. William Tolles Dean of Research Naval Postgraduate School Monterey, CA 93940	1	Mr. G.L. Mackenzie Naval Surface Weapons Center Code R101 Indian Head, MD 20640	1
Naval Research Lab. Code 6100 Washington, D.C. 20375	1	Dr. K.F. Mueller Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1

## DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. J. Murrin Naval Sea Systems Command Code 62R2 Washington, D.C. 20362	1	Dr. A. Nielsen Naval Weapons Center Code 385 China Lake, CA 93555	1
Dr. D.J. Pastine Naval Surface Weapons Center Code R04 White Oak Silver Spring, MD 20910	1	Dr. R. Reed, Jr. Naval Weapons Center Code 388 China Lake, CA 93555	1
Mr. L. Roslund Naval Surface Weapons Center Code R122 White Oak, Silver Spring MD 20910	1	Dr. L. Smith Naval Weapons Center Code 3205 China Lake, CA 93555	1
Mr. M. Stosz Naval Surface Weapons Center Code R121 White Oak Silver Spring, MD 20910	1	Dr. B. Douda Naval Weapons Support Center Code 5042 Crane, Indiana 47522	1
Dr. E. Zimmet Naval Surface Weapons Center Code R13 White Oak Silver Spring, MD 20910	1	Dr. A. Faulstich Chief of Naval Technology MAT Code 0716 Washington, D.C. 20360	1
Dr. D. R. Derr Naval Weapons Center Code 388 China Lake, CA 93555	1	LCDR J. Walker Chief of Naval Material Office of Naval Technology MAT, Code 0712 Washington, D.C. 20360	1
Mr. Lee H. Gilbert Naval Weapons Center Code 3205 China Lake, CA 93555	1	Mr. Joe McCartney Naval Ocean Systems Center San Diego, CA 92152	1
Dr. E. Martin Naval Weapons Center Code 3858 China Lake, CA 93555	1	Dr. S. Yamamoto Marine Sciences Division Naval Ocean Systems Center San Diego, CA 91232	1
Mr. R. McCarten Naval Weapons Center Code 3272 China Lake, CA 93555	1	Dr. G. Bosmajian Applied Chemistry Division Naval Ship Research & Development Center Annapolis, MD 21401	1
		Dr. H. Shuey Rohn and Haas Company Huntsville, Alabama 35801	1

## DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. J.F. Kincaid Strategic Systems Project Office Department of the Navy Room 901 Washington, D.C. 20376	1	Dr. C.W. Vriesen Thiokol Elkton Division P.O. Box 241 Elkton, MD 21921	1
Strategic Systems Project Office Propulsion Unit Code SP2731 Department of the Navy Washington, D.C. 20376	1	Dr. J.C. Hinshaw Thiokol Wasatch Division P.O. Box 524 Brigham City, Utah 84302	1
Mr. E.L. Throckmorton Strategic Systems Project Office Department of the Navy Room 1043 Washington, D.C. 20376	1	U.S. Army Research Office Chemical & Biological Sciences Division P.O. Box 12211 Research Triangle Park NC 27709	1
Dr. D.A. Flanigan Thiokol Huntsville Division Huntsville, Alabama 35807	1	Dr. R.F. Walker USA ARRAOCOM DRDAR-LCE Dover, NJ 07801	1
Mr. G.F. Mangum Thiokol Corporation Huntsville Division Huntsville, Alabama 35807	1	Dr. T. Sinden Munitions Directorate Propellants and Explosives Defence Equipment Staff British Embassy 3100 Massachusetts Ave. Washington, D.C. 20008	1
Mr. E.S. Sutton Thiokol Corporation Elkton Division P.O. Box 241 Elkton, MD 21921	1	LTC B. Loving AFROL/LK Edwards AFB, CA 93523	1
Dr. G. Thompson Thiokol Wasatch Division MS 240 P.O. Box 524 Brigham City, UT 84302	1	Professor Alan N. Gent Institute of Polymer Science University of Akron Akron, OH 44325	1
Dr. T.F. Davidson Technical Director Thiokol Corporation Government Systems Group P.O. Box 9253 Edgen, Utah 84409	1	Mr. J. M. Frankle Army Ballistic Research Labs ARRAOCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005	1

## DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. Ingo W. May Army Ballistic Research Labs ARRADCOM Code ORDAR-BLI Aberdeen Proving Ground, MD 21005	1	Dr. J. P. Marshall Dept. 52-35, Bldg. 204/2 Lockheed Missile & Space Co. 3251 Hanover Street Palo Alto, CA 94304	1
Professor N.W. Tschoegl California Institute of Tech Dept. of Chemical Engineering Pasadena, CA 91125	1	Ms. Joan L. Janney Los Alamos National Lab Mail Stop 920 Los Alamos, NM 87545	1
Professor M.D. Nicol University of California Dept. of Chemistry 405 Hilgard Avenue Los Angeles, CA 90024	1	Dr. J. M. Walsh Los Alamos Scientific Lab Los Alamos, NM 87545	1
Professor A. G. Evans University of California Berkeley, CA 94720	1	Professor R. W. Armstrong Univ. of Maryland Department of Mechanical Eng. College Park, MD 20742	1
Professor T. Litovitz Catholic Univ. of America Physics Department 520 Michigan Ave., N.E. Washington, D.C. 20017	1	Prof. Richard A. Reinhardt Naval Postgraduate School Physics & Chemistry Dept. Monterey, CA 93940	1
Professor W. G. Knauss Graduate Aeronautical Lab California Institute of Tech. Pasadena, CA 91125	1	Dr. R. Bernecker Naval Surface Weapons Center Code R13 White Oak, Silver Spring, MD 20910	1
Professor Edward Price Georgia Institute of Tech. School of Aerospace Engin. Atlanta, Georgia 30332	1	Dr. M. J. Kamlet Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910	1
Dr. Kenneth O. Hartman Hercules Aerospace Division Hercules Incorporated P.O. Box 210 Cumberland, MD 21502	1	Professor J. D. Achenbach Northwestern University Dept. of Civil Engineering Evanston, IL 60201	1
Dr. Thor L. Smith IBM Research Lab 042.282 San Jose, CA 95193	1	Dr. N. L. Basdekas Office of Naval Research Mechanics Program, Code 432 Arlington, VA 22217	1
		Professor Kenneth Kuo Pennsylvania State Univ. Dept. of Mechanical Engineering University Park, PA 16802	1

## DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. S. Sheffield Sandia Laboratories Division 2513 P.O. Box 5800 Albuquerque, NM 87185	1	ONR Resident Representative Ohio State University Res. Ctr. 1314 Kinnear Road Columbus, OH 43212	1
Dr. M. Farber Space Sciences, Inc. 135 Maple Avenue Monrovia, CA 91016	1		
Dr. Y. M. Gupta SRI International 333 Ravenswood Avenue Menlo Park, CA 94025	1		
Mr. M. Hill SRI International 333 Ravenswood Avenue Menlo Park, CA 94025	1		
Professor Richard A. Schapery Texas A&M Univ. Dept of Civil Engineering College Station, TX 77843	1		
Dr. Stephen Swanson Univ. of Utah Dept. of Mech. & Industrial Engineering MEB 3008 Salt Lake City, UT 84112	1		
Mr. J. D. Byrd Thiokol Corp. Huntsville Huntsville Div. Huntsville, AL 35807	1		
Professor G. D. Duvall Washington State University Dept. of Physics Pullman, WA 99163	1		
Prof. T. Dickinson Washington State University Dept. of Physics Pullman, WA 99163	1		

